


The Orion logo consists of the word "orion" in a lowercase, sans-serif font. The letter "o" is a solid blue circle, while the other letters are white with a thin blue outline.

*Delivering sustainable solutions*



## **SPECIALTY CARBON BLACKS FOR PIGMENTED INKJET INKS**

Technical Information 1291

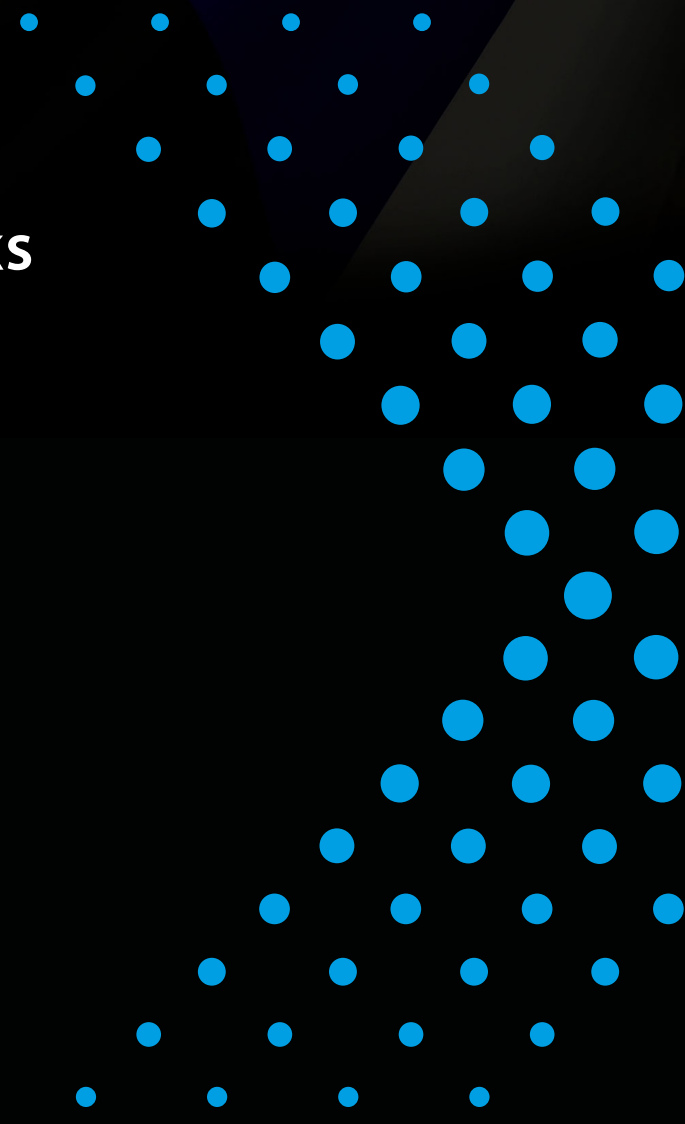

## CONTENTS

<b>1 INTRODUCTION</b>	<b>2</b>
<b>2 THE CARBON BLACK PROCESS</b>	<b>3</b>
2.1 The furnace black process	3
2.2 The gas black process	4
2.3 Comparison between the furnace black and gas black process	4
<b>3 SPECIALTY CARBON BLACK PRODUCT PORTFOLIO FOR INKJET INKS</b>	<b>5</b>
<b>4 DISPERSION AND STABILIZATION OF SPECIALTY CARBON BLACKS</b>	<b>7</b>
4.1 Dispersion equipment	8
4.1.1 Dissolver	
4.1.2 Rotor-stator	
4.1.3 Lab dispersing equipment	
4.1.4 Bead mills/agitator ball mills	
4.1.5 High-pressure dispersion equipment	
4.2 Process of specialty carbon black dispersions and final inkjet inks	10
<b>5 EVALUATION OF DISPERSIBILITY AND OPTICAL DENSITY</b>	<b>11</b>
5.1 Particle size	11
5.2 Storage stability	12
5.3 Optical density	13
<b>6 SUMMARY</b>	<b>15</b>

## 1 INTRODUCTION

Pigment based inkjet inks have assumed leading market positions in desktop as well as wide-format inkjet printing since they provide outstanding light- and water-fastness as well as superior optical densities.

Among black pigments, Orion's specialty carbon blacks have become the state of the art in inkjet ink pigments. Irrespective of the print head technology, they allow the formulation of inkjet inks to meet the highest requirements in today's home use-, small office-, commercial- and industrial inkjet ink application.

The purpose of this Technical Information is to illustrate Orion's broad range of NIPex® specialty carbon black powders and to provide the formulator with the essential information for the successful development of technically and commercially superior inkjet inks.

## 2 THE CARBON BLACK PROCESS

Specialty carbon blacks are manufactured by the partial combustion of hydrocarbons to form individual carbon black particles. The conditions in the process are such that the newly created particles collide and fuse together within fractions of a second. This results in the formation of branched, chain-like aggregates with a size above 100 nm. The aggregates are the smallest dispersible unit of a specialty carbon black (**figure 1**). The aggregates, via mechanical entanglement, form loose collections of larger structures commonly referred to as agglomerates. In contrast to the sub-micron size of the aggregates, the more friable agglomerate structure can range in size from one to several hundred microns.

Since agglomerates are only bound through weak forces, they are easily broken down by shear forces during processing, so that the aggregates are the dominant particle species in an ink formulation.


### 2.1 The furnace black process

The furnace black process (**figure 2**) uses liquid hydrocarbons as feedstock. The feedstock is injected into a refractory-lined furnace, which is heated by the combustion of natural gas and pre-heated air.

After the specialty carbon black is formed, it is quenched by water, cooled down and separated from the gas stream. The main advantage of the furnace black manufacturing process is its flexibility to tailor carbon black properties such

**Figure 1**


Scanning electron microscopic image of a carbon black aggregate (120,000x magnification)

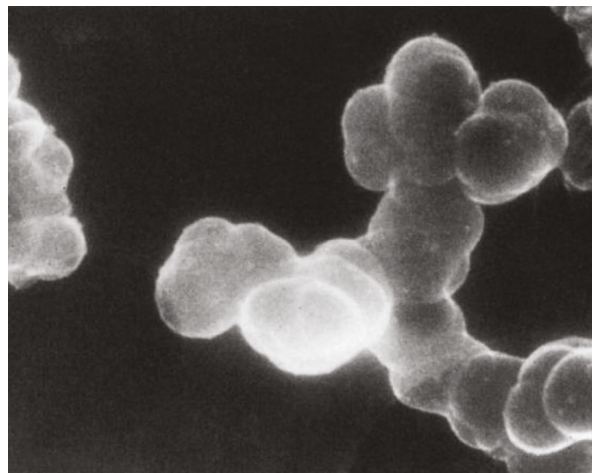

as average primary particle size (between 10 and 80 nm), degree of aggregation, aggregate size distribution, and porosity. Furnace blacks usually carry a small amount of basic functional groups on their surface and therefore exhibit a hydrophobic, non-polar character, along with a pH value above 7. Post-oxidation processes allow tailored modification of these surface characteristics.

**Figure 2**

Schematic depiction of the furnace black manufacturing process

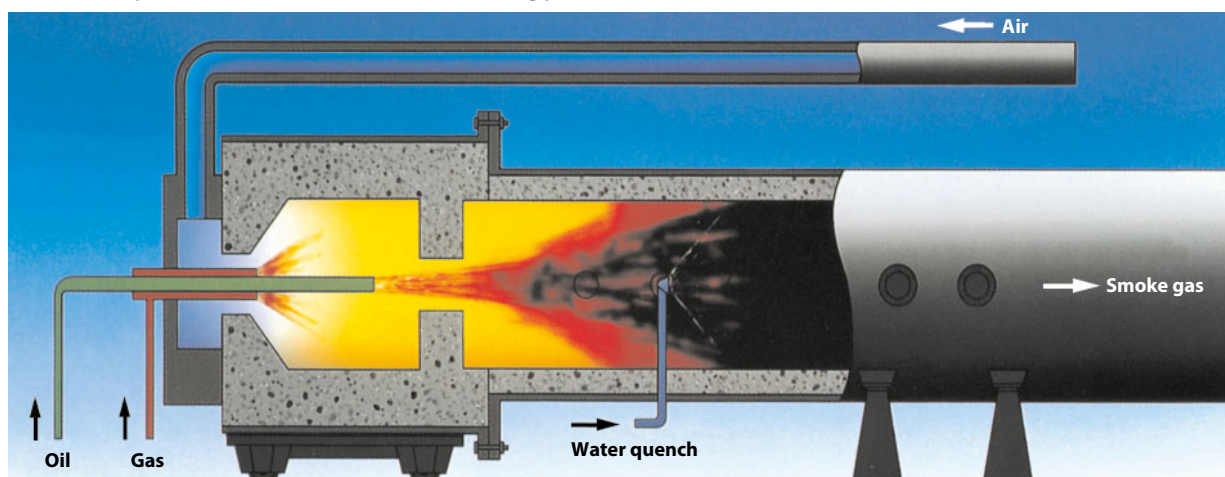

## 2.2 The gas black process<sup>1)</sup>


The gas black process (**figure 3**) derives its name from the fact that the feedstock is vaporized and fed to the combustion chamber by means of a carrier gas. This vaporization step prevents the contamination of the specialty carbon black with feedstock residues and results in a low ash product. During the burning phase, the presence of oxygen ensures a high degree of oxygen-functional groups on the pigment surface. These polar groups account for the acidic pH range of all gas blacks.

Some of the important properties of gas blacks are:

- Primary particle size between 10 and 30 nm
- Narrow primary particle and aggregate size distribution
- High purity
- Very high structure that is easily dispersed

**Figure 3**

Schematic depiction of the Degussa gas black process

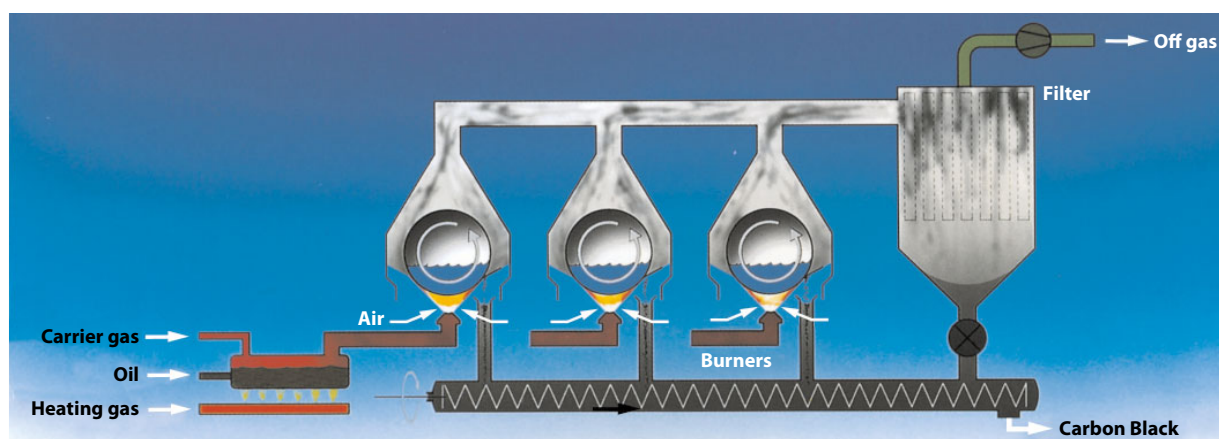

## 2.3 Comparison between the furnace black and gas black process<sup>1</sup>

The key differences of specialty carbon blacks produced by the furnace black and gas black processes are summarized in **table 1**.

**Table 1**

Key differences between furnace blacks and gas blacks


GAS BLACK PROCESS	PROCESS	FURNACE BLACK PROCESS
Open oxidizing atmosphere	Process conditions	Closed reducing atmosphere
Very high but loose structure	Structure	Variable
Many acidic groups	Surface oxides	Few basic groups
Acidic (3.5 – 4.5)	pH value	Basic (8 – 10)
Hydrophilic, polar	Water wettability	Hydrophobic, non-polar

Examples of oxygen-functional groups on the carbon black surface which can be created in the two different carbon black processes depicted in **figure 4**.

<sup>1)</sup> according to the Degussa gas black process

**Figure 4**

**Surface functional groups on specialty carbon black**

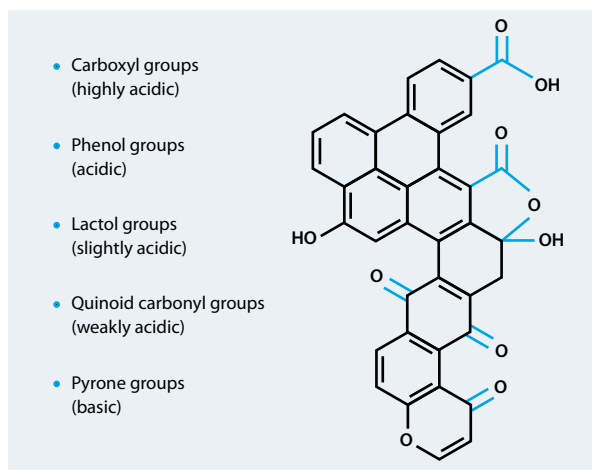


Predominantly, acid groups are formed on the gas black particle surface due to the presence of ambient air during the burning phase of the gas black process. In contrast, only a few surface oxides are formed on the furnace black particle surface. These particles are predominantly basic in character due to the furnace black process being closed and void of excess oxygen. Orion offers a broad range of specialty carbon black grades produced by both processes. This enables us to supply specialty carbon blacks with tailored surfaces for individual requirements. Hydrophilic grades with polar surface properties, for example, are especially suitable pigments for water-based inkjet inks while hydrophobic products are preferred for non-polar solvent based inks.

### 3 SPECIALTY CARBON BLACK PRODUCT PORTFOLIO FOR INKJET INKS

Orion's specialty carbon blacks, produced by its unique gas black process and marketed under the tradename NIPex® IQ, are the preferred choice for water-based inkjet inks. Due to their high structure and surface polarity, gas blacks re-agglomerate while the ink is drying and form large network-like agglomerates on the substrate, making them well-suited for printing on plain paper (see figure 5). The re-agglomeration limits pigment penetration into the substrate and is the key factor for the outstanding optical densities. Additionally, our NIPex® IQ grades meet the highest demands of the inkjet industry regarding quality and purity (see also table 2).

**Figure 5**

**Transmission electron microscopic image (microtome section) of plain paper printed with a gas black-based Inkjet Ink**

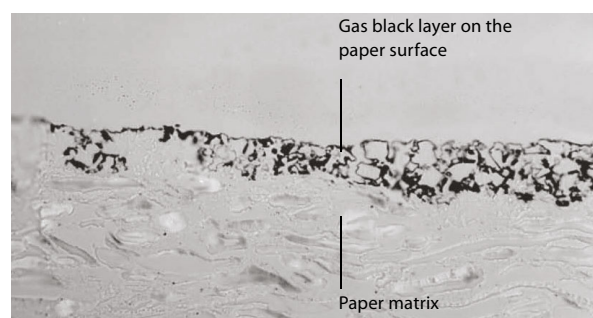

**Table 2**

**Benefits of NIPex® IQ gas blacks in inkjet printing**


<b>GAS BLACK PROPERTIES</b>	<b>APPLICATION BENEFITS</b>
High concentration of oxygen-functional surface groups	Good wettability and easy dispersability in water and other polar media
High degree of purity	Minimizes corrosion and deposits on the print head, better colloidal stability
High but loose structure	Easy dispersability
Pigment aggregates can agglomerate to form a larger network structure	Prevents pigment penetration into porous printing media resulting in high optical density values

The gas blacks NIPex® 160 IQ, NIPex® 170 IQ and NIPex® 180 IQ are manufactured as described in chapter 2.2 without a subsequent post-treatment. They differ from each other in their mean primary particle sizes and specific surface

areas. They are the first choice when developing a new water-based inkjet ink formulation. The high purity combined with the high structure provides excellent printability and high optical density especially on plain paper. result in low viscosity of the final inkjet ink.

**Figure 6**

**Overview about Orion's specialty carbon blacks for inkjet inks**

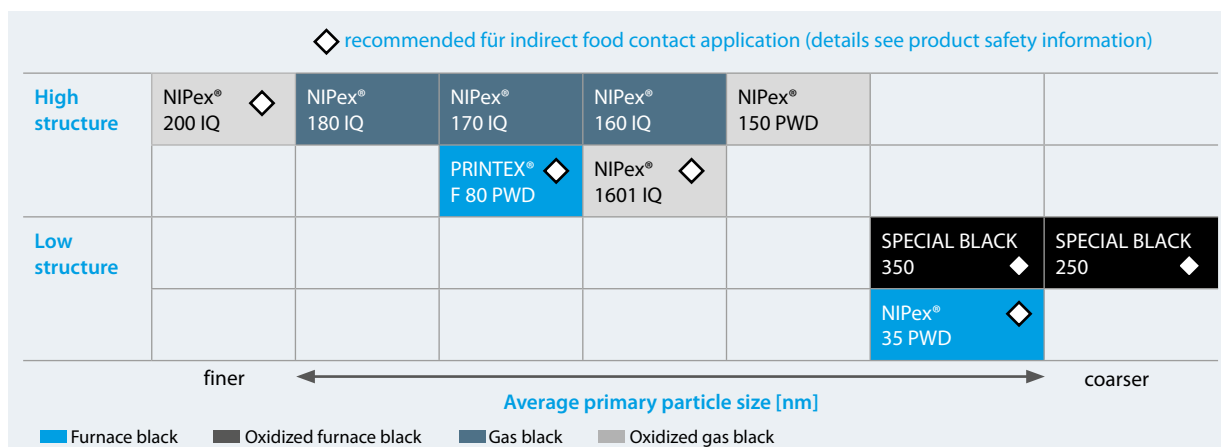

**Figure 7**

SPECIALTY CARBON BLACK	AVERAGE PRIMARY PARTICLE SIZE	BET SURFACE AREA	OIL ABSORPTION NUMBER (OAN)	VOLATILE MATTER AT 950°C	PH VALUE	DIGITAL FOOD PACKAGING INKS	AQUEOUS INKJET INKS	NON-AQUEOUS INKJET INKS	UV CURING INKJET INKS
	nm	m <sup>2</sup> /g	ml/100g	%					
NIPex® 200 IQ	13	580	160	20	2.3	◇	◇		
NIPex® 180 IQ	15	260	140	5	4.5		◇		
NIPex® 170 IQ	17	238	135	5	4.5		◇		
NIPex® 160 IQ	20	180	128	5	4.5		◇		
NIPex® 1601 IQ	20	245	128	10	4.0	◇	◇		
PRINTEX® F 80 POWDER	16	225	105	1.2	9.5	◇	◇		
NIPex® 150 POWDER	25	175	120	10	4.0			◇	
SPECIAL BLACK 350	31	62	43	1.4	3.5	◇		◇	◇
NIPex® 35 POWDER	31	60	42	0.5	9.0	◇		◇	
SPECIAL BLACK 250	47	48	45	1.4	3.5	◇			◇

An overview of Orion specialty carbon blacks for inkjet inks is given in figure 6 and 7. Additionally, a broad range of other specialty carbon black grades is available which mainly differ in primary particle size, degree of oxidation, porosity and structure.

Detailed information about these specialty carbon black grades is described in Orion brochure "What is carbon black". Specialty carbon black grades for UV curing ink systems are introduced in detail in Technical Information TI 1257.

## 4 DISPERSION AND STABILIZATION OF SPECIALTY CARBON BLACKS

The proper dispersion of a specialty carbon black is the most challenging step in producing a high quality inkjet ink. Orion has extensive experience and in-depth knowledge of dispersing technologies and colloidal chemistry essential to produce stable, dispersed particles. Our goal is to apply our expertise to assist our customers in producing superior inkjet inks.

**The dispersion process can be divided into three steps:**

- a Wetting of the pigment particles
- b Milling/breaking-down of the agglomerates
- c Stabilization of the aggregates

Wetting is the creation of surface contact between the ink medium (solvent) and pigment. This process can be accelerated by the addition of wetting agents (dispersants) to lower the surface tension of the medium and facilitate spreading the medium onto the pigment surface.

In the next step, cohesive forces within the pigment particle must be overcome to break down the agglomerates into aggregates. This can be accomplished using high energy processing, such as crushing, shear or impact (see chapter 4.1). These mechanical forces are generally sufficient to get the aggregate level, however, they are not high enough to break down the aggregates to primary particles.

In order to stabilize the aggregates dispersed in the ink medium, surface-active substances (dispersants) are typically required. These dispersion additives selectively prevent re-agglomeration of the pigment particles. The potential disadvantage of dispersants is their negative impact on important ink properties.

**The key to developing a successful dispersion is the stabilization method employed. The following methods are frequently used for pigment stabilization in inkjet inks:**

- Electrostatic stabilization
- Sterical stabilization

Electrostatic stabilization is based on the adsorption of ionic dispersion additives at the carbon black surface. This creates a charged double layer and causes the charged pigment


**Table 3**

**Advantages and disadvantages of electrostatic and sterical stabilization of specialty carbon blacks for use in inkjet inks**

	BENEFITS	WEAKNESSES
Electrostatic stabilization	<ul style="list-style-type: none"><li>• High stability</li><li>• Reduced tendency to foam</li></ul>	<ul style="list-style-type: none"><li>• pH dependence on the ionic strength</li><li>• Reduction of the surface tension</li><li>• Dispersion instability in the presence of multivalent cations</li></ul>
Sterical stabilization	<ul style="list-style-type: none"><li>• Improved adhesion properties</li><li>• Good compatibility with ink additives</li></ul>	<ul style="list-style-type: none"><li>• Tendency to foam</li><li>• High viscosities</li><li>• Ink encrustation of the inkjet printer nozzles and/or deposits in the print head</li></ul>

**Figure 8**

**Ink encrustation of inkjet printer nozzles**

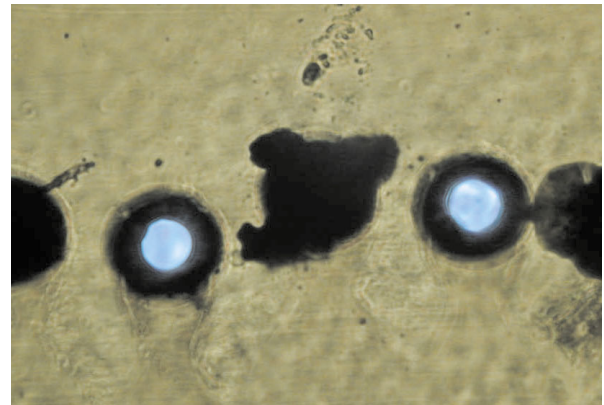

**Figure 9**

**Deposits in the ink supply to the print head heat elements**



particles to develop strong electrostatic repulsive forces between one another. Excellent results can be obtained with dyes as the function of anionic dispersant, an area where Orion has strong know-how and experience.

Steric stabilization results from the adsorption of polymeric and/or non-ionic dispersion additives at the surface of a carbon black. This creates a barrier or "separator" between pigment particles that prevents re-agglomeration. In inkjet inks, polymer molecules are predominantly used for steric stabilization.

The trend in inkjet print-head technology is towards smaller droplets, which requires print-head nozzles with diameters of just a few micrometers. Prevention of nozzle clogging and deposits on the print-head is essential to ensure long-term print reliability. Particle fineness of the pigment, purity of ink ingredients and long term stability of the ink dispersion are necessary requirements. A key role is hereby played by the specialty carbon blacks which need to fulfill the following requirements:

- Excellent dispersability and dispersion stability in ink solvents
- High optical density on uncoated and coated substrates
- High purity

The dispersibility of a carbon black is strongly influenced by its primary particle size, structure, porosity and amount of surface oxides. Specialty carbon blacks with large primary particles, high structure and porosity and a high number of surface oxides are the most easily dispersible products.

#### 4.1 Dispersion equipment

As explained in the previous chapter, the agglomerates of specialty carbon blacks can be efficiently broken up by shear, crushing or impact. Type and intensity of the respective force depends on the dispersion equipment used.


Shear occurs when forces exerted on a large agglomerate have opposing directions as a result of, for example, different flow speeds of the surrounding medium. If the shear force is high enough to overcome the adhesion energy within the agglomerate, it will rupture (process A in **figure 10**).

Crushing takes place when an agglomerate is broken down between colliding or grinding elements (process B). The term impact is used if the agglomerate collides against the wall of the vessel, a grinding element or another particle and breaks up as a result of this collision (process C).

Usually, a large portion of the energy supplied to the system is dissipated in the form of heat, so efficient temperature control and cooling is recommended during pigment dispersion.

**Figure 10**

**Processes used to break down specialty carbon black agglomerates into aggregates: A shear, B crushing and C impact**

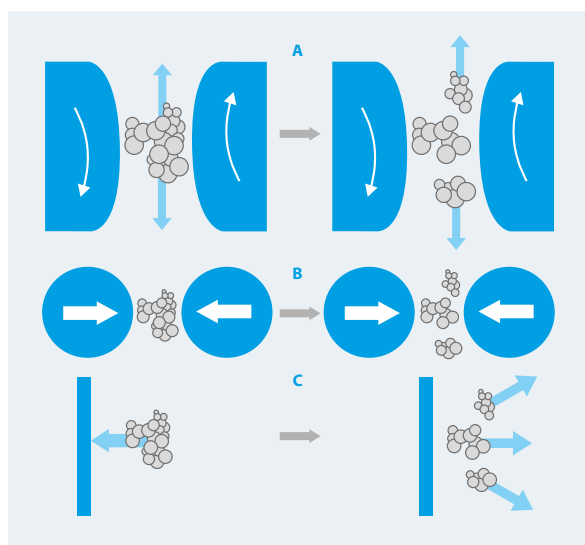

##### 4.1.1 Dissolver

The action of the dissolver depends mainly on shear as a result of speed. The dissolver is the weakest dispersion device in the series described here. The following conditions should be fulfilled to obtain an optimum result (see also **figure 11**):


- A peripheral speed of the disk of 18 – 25 m/s
- The diameter of the vessel should be 2 – 3 times larger than the diameter of the disk
- The distance the dispersion disk from the base of the vessel should be 0.5 – 1 times the diameter of the disk.

##### 4.1.2 Rotor-stator

The dispersion of pigments by means of a rotor-stator is also primarily based on shear.


**Figure 11**

**Optimum geometry for a dissolver disk (left) and photograph of a dissolver disk (right)**

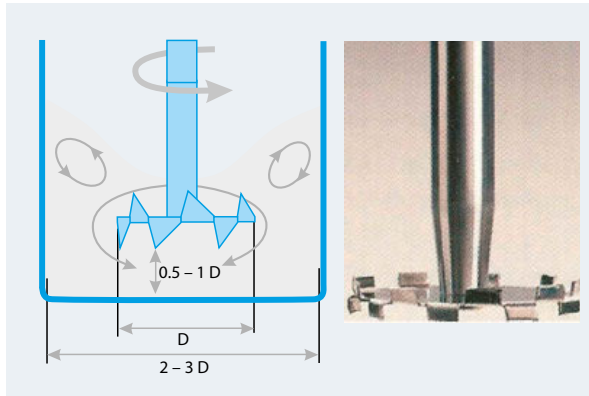

**Figure 12**

**Schematic depiction of the dispersion process by means of a Rotor-stator Stirrer (left). Rotor-stators from two different Manufacturers (middle and right)**

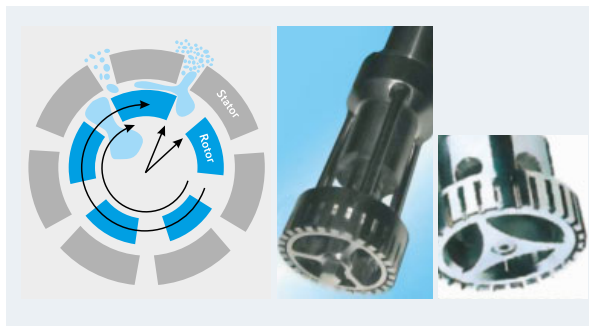

During the dispersion process, liquid and pigment particles are inducted between the stationary stator disk (**figure 12**, left picture; depicted in grey) and the rotating rotor disk inside the rotor-stator stirrer depicted (in blue). The narrow gap between rotor and stator, combined with the high rotating speed of the rotor, results in high shear forces. This shearing energy can be controlled by varying the speed of rotation.

#### 4.1.3 Lab dispersing equipment

Ultrasonic dispersers with high power (>500 Watt) are often used for lab screening tests to prepare small quantities of specialty carbon black dispersions. The mechanism of ultrasonic dispersers is also based on the shear principle. The forces necessary for the dissociation of the particles are produced by pressure differences.

An ultrasonic unit consists of a sound generator, sound transducer and sonotrode. The generator produces electrical vibrations in the ultrasonic range (> 20,000 vibrations/min), which are converted by the transducer into mechanical vibrations. Depending on equipment, the high energy input can lead to pronounced warming

of the sample. A drawback of ultrasonic dispersion is the noise and the wear of the sonotrode which limits the use in production scale.

**Figure 13**

**Typical laboratory dispersing equipment: Shaking Mixer Skandex (A) and ultra sound dispersion equipment (B)**



Shaking mixers are devices in which the dispersion mixture is subjected to intensive shaking in a closed container. Grinding elements, usually in the form of beads, are added to the mixture to increase the input of energy. Agglomerates are thus broken down by shear, impact and crushing. Shaker mixers allow the preparation of high quality dispersions but the method is restricted to laboratory use.

#### 4.1.4 Bead mills/agitator ball mills

Bead mills and agitator ball mills are similar types of equipment.

The cylindrical or conical agitator chamber consists of the agitator shaft with grinding disks. The mill chamber contains the material to be milled and the grinding beads, which are set in motion by the rotation of the agitator shaft, causing the pigment agglomerates to be broken up (**figure 14**). The bulk of the dispersion work is achieved by shearing in the immediate vicinity of the agitating elements. A separating device holds the grinding beads in the mill and redirects them via a channel to the inlet of the mill chamber.

Today's modern bead mills are available in various sizes and configurations such as horizontal or vertical operating positions, different types of agitators/stators, bead separators and cooling systems which enables the selection of tailored wet-grinding technology. The number of variable parameters is large and it is necessary to optimize them for good grinding results:

- Operating parameters such as agitator speed, throughput, filling rate of the beads, single or multi-pass or circulation process
- Design, material and size of the bead mill

- Grinding elements such as type, size, etc.
- Ratio of cooling surface to volume of mill chamber
- Separation technology of grinding elements
- Composition of formulation, such as solid content, liquid medium, dispersants or additives to optimize viscosity and surface tension, and additives to minimize the risk of crusting and foaming during grinding process.

#### 4.1.5 High-pressure dispersion equipment

In the late 1980's, the first patent was published reporting the dispersion of a pigmented ink-jet ink by passing through at least a plurality of nozzles within a liquid jet interaction chamber at a liquid pressure of at least 1,000 psi. During processing, the product stream accelerates to very high velocities, creating shear rates of much higher magnitude. Such dispersion equipment as described above is supplied by Microfluidics under the tradename Microfluidizers.

Microfluidizers are offered with pressure ranges up to 40,000 psi. An array of nozzles allow the jetting of liquid streams, directed towards each other and at high velocities. The high energy particle collisions that occur result in dispersions having a narrow distribution of very fine particles. Alternative high-pressure homogenizers operate by pushing dispersions through variable geometry spring loaded valves at high pressures (up to 15,000 psi). Such homogenizers are also often used for milk homogenization at 2,000 to 3,000 psi. Their main drawback is the limitation of process pressure as well as the spring-loaded valve which does not allow precise particle size control.

The main advantages of high-pressure dispersion equipment include:

- Very effective dispersing method to obtain small carbon black aggregates
- Fast processing times
- Control of energy input by process pressure
- Reduced contamination (absence of bead abrasion)
- Very low batch to batch process variation

**Figure 14**

**Bead mill**



#### 4.2 Manufacturing process of specialty carbon black dispersions and final inkjet inks

Although pigment dispersions can be produced with different dispersing equipment, bead mills are most commonly used for manufacturing specialty carbon black dispersions.

Generally, it is recommended to manufacture a specialty carbon black dispersion for an inkjet ink using the following four process steps (**figure 15**):

##### **Step 1: Pre-dispersion**

It is highly recommended to mill the pigment preparation with high pigment loading. This reduces the risk of contaminating the milled pigment dispersion through bead abrasion and increases the milling energy input into the product. Usually gas blacks can be milled with a pigment loading of about 25 – 30% by weight depending on the pigment surface, dispersing agents and surface chemistry

**Figure 15**

**Process steps to prepare a specialty carbon black dispersion for inkjet inks**



De-ionized water and all other components except carbon black are filled into the vessel. Carbon black is slowly added while stirring with a dissolver or rotor-stator at low rpm. Once the carbon black is completely wetted out, the speed of the dissolver is increased until optimum homogenization is obtained. Mixing time with the dissolver is typically 20 minutes or more.

To prevent evaporation of water and/or solvents and hence crusting of the mill base, it is recommended to cover all containers during the pre-dispersion process.

### **Step 2: Grinding process**

The grinding process should be carried out in a closed media mill in recirculation mode. Therefore the milling base prepared in step 1 is pumped through the media mill and back to the container with high velocity of circulation. Depending on the efficiency of the media mill and the dispersion composition, the grinding process is usually best carried out with a spe-

cific grinding energy in the range of 100 – 300 kWh/t. The grinding quality of the dispersion can be determined by a light microscope at 200 to 500 fold magnification. Grinding is completed if no particles bigger than 1 µm can be detected in the dispersion. If larger particles are still present in the dispersion, the milling process should be continued. The bead mill should meet the following criteria:


- Grinding media: 0.3 mm to maximum 1.0 mm
- Grinding media material: Zirconium oxide (preferably Yttrium doped Zirconium oxide)
- Rotor and stator material: lowest possible abrasive properties

### **Step 3: Dilution of the mill base**

After preparation of the mill base in step 2, the pigment dispersion is diluted to the final inkjet ink in a separate container. Before starting the dilution process the specialty carbon black content of the mill base should be determined to enable an accurate adjustment of the pigment loading in the final inkjet ink.

**Figure 16**

**Dilution of the mill base to the final dispersion and/or inkjet ink: improper (left) and correct process (right) to prevent dispersion shock**

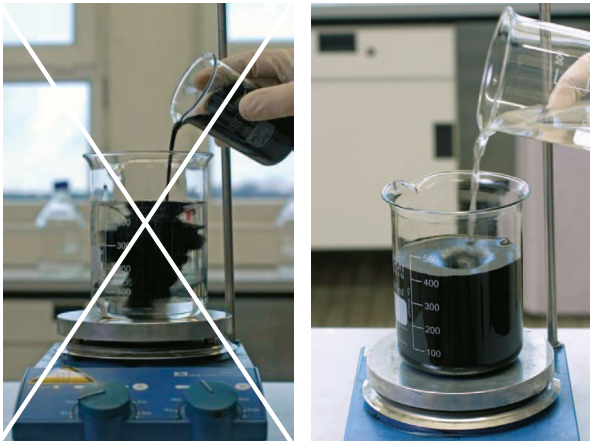

Parallely a premix is prepared containing all other dispersion and/or ink additives. This additive mixture is then slowly and carefully added to the mill base by stirring with a propeller mixer. It is critical to prevent a “dispersion shock” during the dilution step which may cause pigment flocculation. Therefore it is highly recommended to add the additive premix into the pigment concentrate and not the other way around as shown in **figure 16**.

#### **Step 4: Filtration of pigment dispersion and/or final inkjet ink**

High efficiency polypropylene filters from 0.3 to 1.0  $\mu\text{m}$  fineness are recommended to filter pigment dispersions and final pigmented inkjet inks. The main objective of the filtration step is to remove large particles and enable maximum print performance.


## **5 EVALUATION OF DISPERSIBILITY AND OPTICAL DENSITY**

### **5.1 Particle size**

Examination of a dispersion sample with a transmission light microscope at 500-fold magnification allows a quick characterization of the dispersion quality, since coarse particles can be easily detected (**figure 17**). Further valuable information on the dispersion quality and particle size distribution can be obtained by static laser light scattering measurements.

**Figure 17**

**Light microscopy images of good (left) and poor (right) carbon black dispersion.**

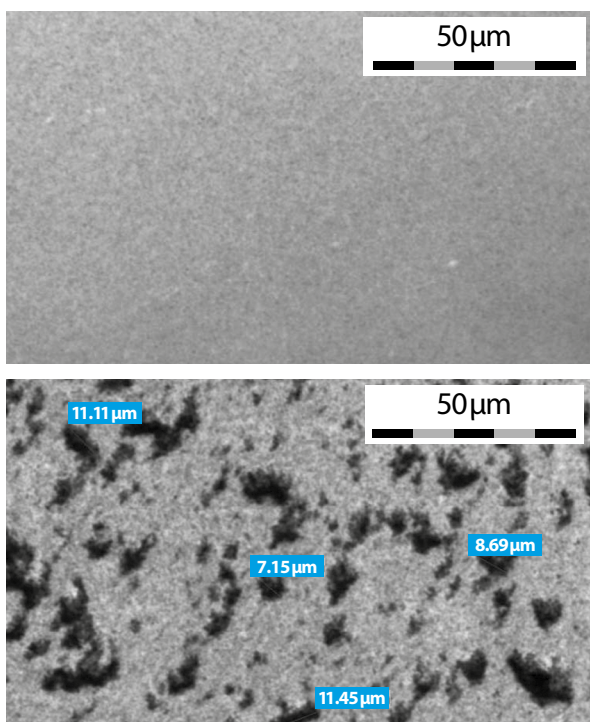

Filtration can be used as an efficient, practical, application-related test to determine the dispersibility of specialty carbon black. The filtrate volume of a specialty carbon black dispersion (diluted to 5% pigment content) at a defined pressure is measured. The amount of filtrate strongly depends on the concentration of coarse particles in the dispersion.

### **5.2 Storage stability**

Several stability test methods are usual to determine the dispersity of specialty carbon black dispersions and final pigmented inkjet ink. Common methods include:

- Zeta potential measurement to determine the surface charge as a function of pH
- Stability tests at elevated temperatures to simulate the long-term stability at room temperature
- Freeze-thaw-stability
- Determination of sedimentation profiles by Brookfield Viscometer with a Helipath attachment (**figure 18**)
- Determination of coarse particles content by particle size analyzers


Long term stability tests are an essential attribute for the dispersibility of pigment concentrates and final inkjet inks. Stability testing is conducted on the undiluted dispersion samples at various elevated temperatures over several

weeks. Beside particle size distribution profiles the critical elements are rheological properties, pH stability and sedimentation tendency.

A relevant measurement to determine the stability of specialty carbon black dispersions is the use of a Brookfield viscosimeter with a Helipath attachment. After completing a set storage time at defined conditions, the Brookfield spindle is immersed into the dispersion. The spindle is moved with the Helipath attachment from top to bottom of the flask and back to the starting position with 50 viscosity values being measured during this movement. Viscosity fluctuation between the 50 measuring points is a sign of instability or sedimentation tendency.

**Figure 18**

**Sedimentation profile of specialty carbon black dispersion based on NIPex® 160 IQ after storage for 35 days at 50°C**

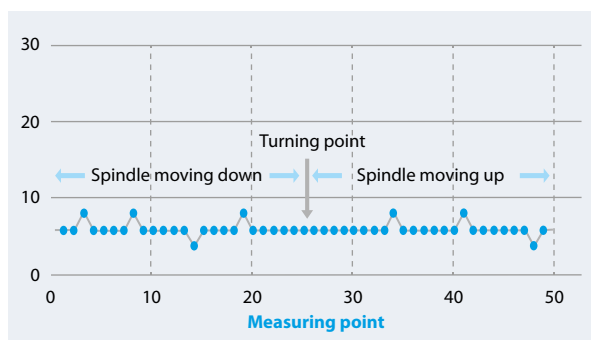

### 5.3 Optical density

Optical density of pigmented inkjet inks on coated papers is primarily obtained by the quality of the paper coating. The paper coating guarantees that the pigment particles build a pigment layer on the paper surface which develops the high optical density. This situation is different for uncoated papers as the finely dispersed specialty carbon black particles can penetrate into the paper pores, decreasing the optical density of the printed text or image. Preventing penetration into uncoated paper is the challenge for ink formulators. Additionally, inkjet inks containing additives with good wetting properties such as dispersants, accelerate the pigment penetration as soon as the inkjet ink is fired onto the paper surface. The result is lower optical densities.

Therefore the selection of specialty carbon black which are easily dispersed is essential to reduce or eliminate wetting agents such as dispersants. A portfolio of oxidized specialty carbon black grades is currently being developed to help customers to meet these needs. Lab tests with model inks, formulated with 3-5 weight % pigment content, are applied to different inkjet and plain papers at a thickness of 6 µm (**figure 19**). After drying, the optical density of these draw-downs is determined with a commercial spectral photometer.

The following parameters are known to have a significant effect on the resulting optical density values from a specialty carbon black preparation:


- Choice of pigment
- Pigment loading
- Choice of dispersants
- Substrate
- Inkjet ink composition

The critical specialty carbon black properties to consider for obtaining high optical density values are:

- High structure (OAN >90 ml/100 g)
- Fine primary particle size ( $\leq 20$  nm)
- High porosity
- Network-like reagglomeration on the substrate surfaces  
(see chapter 3, **figure 5**)

**Figure 19**

Creation of ink draw-downs with a control coater from Erichsen GmbH for the determination of the optical density

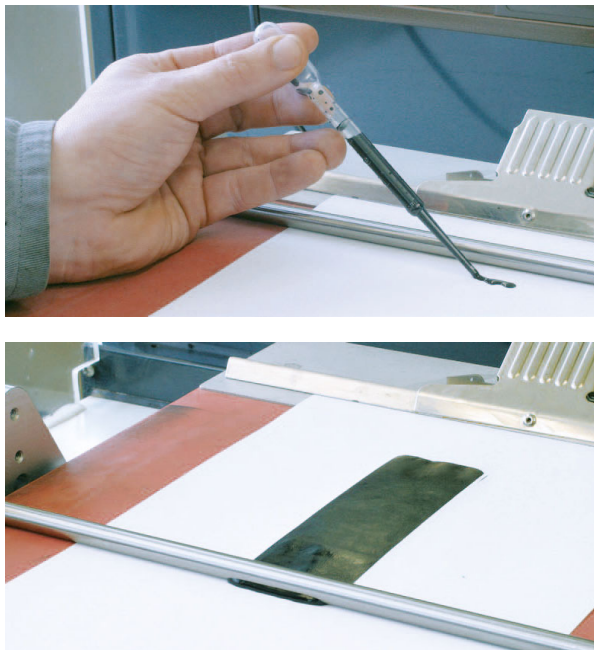

Another critical component of an inkjet ink is the choice of dispersant to meet the demands of a modern inkjet printing system (see chapter 4). While thousands of dispersants are available, only few of them can be used in inkjet inks without decreasing print reliability and image performance. Several patents report using dyes as effective dispersants to stabilize specialty carbon black for inkjet inks, as well as using styrene acrylates or non-ionic dispersants with defined molecular weights.

Simply formulated specialty carbon black dispersions based on NIPex® 160 IQ gas black and dispersants in de-ionized water demonstrate the key role of dispersant, specialty carbon black loading and substrate (see table 4).

**Table 4**

Test inkjet ink formulation


DISPERSION SAMPLE NO.		1	2	3
NIPex® 160 IQ	%	15.0	15.0	15.0
Dispersant A (Dye based dispersant)	%	1.2	–	–
Dispersant B (Styrene acrylate based dispersant)	%	–	14.0	–
Dispersant C (Fatty alcohol ethoxylate based dispersant)	%	–	–	10.0
2-Amino-2-Methyl-Propanol (90 wt. % aqueous solution)	%	–	–	0.3
De-ionized water	%	83.8	71.0	74.7

Optical densities on 6 µm draw downs were determined for three dispersions diluted to 4.0% NIPex® 160 IQ weight content with de-ionized water.

The tremendous influence of the dispersant on the optical density is shown in figure 20. Dispersion sample no. 3, containing a fatty alcohol ethoxylate based dispersant, results in poor optical density on all plain paper types. The result is due to the excellent wettability of this dispersant, preventing the agglomerate network to form and allowing the fine carbon black aggregates to penetrate into the pores of plain paper.

**Figure 20**


Influence of dispersants and substrate on the optical density of specialty carbon black dispersions based on 4.0% NIPex® 160 IQ (compare to table 4)

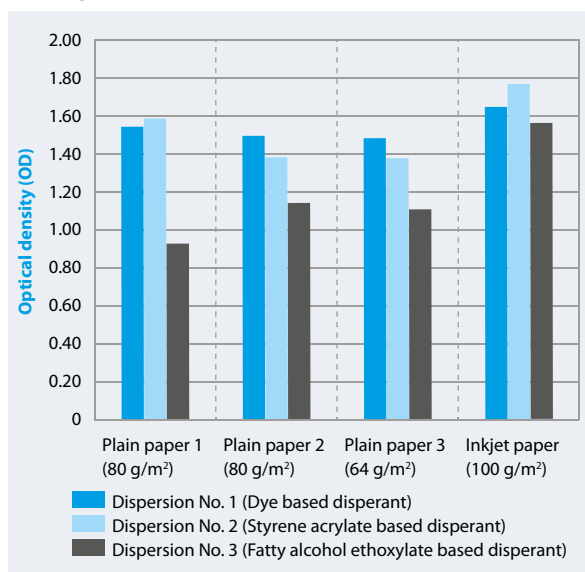

A combination of choosing the best specialty carbon black, substrate and dispersant provides high optical density. This can be even further improved by the specialty carbon black content as shown in figure 21. Beside these key parameters, surface tension, viscosity, and ink additives offer further opportunities for achieving high optical density.

**Figure 21**

Influence of carbon black content on the optical density of specialty carbon black dispersion No. 2

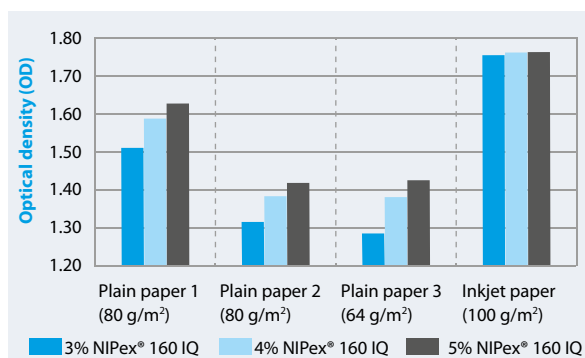

## 6 SUMMARY

This technical information gives an overview about specialty carbon black manufacturing processes, dispersion preparation, selected specialty carbon blacks for different inkjet ink formulation and influences of several parameters such as dispersants, substrates and specialty carbon blacks itself on applied technical properties of final inkjet inks. Orion offers a broad portfolio of specialty carbon blacks based on furnace black and gas black process which are tailored in regard to purity, particle fineness, structure and surface chemistry to meet inkjet ink requirements.

Some key guidelines about the right choice of specialty carbon blacks are as follows:

- Gas blacks such as NIPex®IQ grades are tailored for waterborne inkjet inks because of the ease of dispersion, high amount of surface oxides (very polar surface) and high structure which prevents pigment penetration into absorptive substrates.
- In case of highest purity requirements for indirect food contact application PRINTEX®F80 PWD fulfills food packaging regulation as well as compliance of FDA regulation, 21 CFR sec. 178.3297 "Colorants for polymers". NIPex® 1601 IQ, NIPex 200 IQ, NIPex 35 PWD, SPECIAL BLACK 250 and SPECIAL BLACK 350 are other candidates which are in compliance with food packaging regulation.
- Detailed information about compliance status and product safety relevant data are available in separate product safety information for each grade.
- For UV curing inkjet inks coarser, low structured and surface-treated specialty carbon blacks such as SPECIAL BLACK 250 and SPECIAL BLACK 350 are recommended for first orientation tests. These grades offer best compromises between good cure speed, high optical density and gloss as well as low viscosity requirements.
- Best choice of specialty carbon black for non-aqueous inkjet inks strongly depends on several parameters such as dispersing process, dispersants, binder system or polarity of solvents used. We can offer a broad portfolio starting from NIPex®150 PWD with high surface polarity to NIPex®35 PWD with hydrophobic behaviour to find the optimum specialty carbon black solution.
- For further information please contact our Technical Market Managers responsible for printing systems.

## THE AMERICAS

Orion Engineered Carbons LLC  
1700 City Plaza Drive, Suite 300  
Spring, TX 77389  
USA  
Phone +1 832 445 3300  
AMERICAS@orioncarbons.com

## EUROPE/ MIDDLE EAST/ AFRICA

Orion Engineered Carbons GmbH  
Frankfurter Straße 60 - 68  
65760 Eschborn  
Germany  
Phone +49 6196 771 929 100  
EMEA@orioncarbons.com

## ASIA PACIFIC

Orion Engineered Carbons (China) Investment Co., Ltd.  
Room 2301, 2302, 2307, BM InterContinental Business Center  
100 Yutong Road, Jing'an District, Shanghai 20007  
P. R. China  
Phone +86 21 6107 0966  
APAC@orioncarbons.com

## INCORPORATED IN LUXEMBURG

Orion S.A., 6, Route de Trèves, 2633 Senningerberg, Luxembourg, Phone +352 270 48 06 0

All statements and information given herein by Orion Engineered Carbons GmbH as well as its affiliates, including for example **Orion S.A. ("Orion")**, are provided for information purposes only and are provided as of the date of this document. They are based on the knowledge of Orion on the date of the document. ORION DOES NOT GIVE ANY REPRESENTATION OR WARRANTY THAT THE CONTENTS OF THE GIVEN STATEMENTS AND INFORMATION ARE CORRECT OR ACCURATE. ANY LIABILITY OF ORION WITH REGARD TO THE CONTENTS PROVIDED ARE HEREBY EXPRESSLY EXCLUDED. Orion does not give a warranty or makes any representation with respect to any results to be obtained from such statements or information, any uses of such information or with regard to the non-infringement of any proprietary right. Nothing stated herein shall be construed as a license of or recommendation for use, especially with concern to the potential infringement of any proprietary right. Use or application of such information or statements or the material or systems described herein are at user's sole discretion and risk. The user acknowledges that Orion shall bear no responsibility or liability for any use or application of such information or statements or the material or systems described herein. All sales are subject to the respective standard terms and conditions of sale and delivery issued by Orion including but not limited to the limitation of liability contained therein. The Orion standard terms and conditions of sale and delivery (English) can be reviewed, downloaded and printed under [https://orioncarbons.com/legal/compliance-guidelines/#terms\\_conditions](https://orioncarbons.com/legal/compliance-guidelines/#terms_conditions).

**Any and all information disclosed by Orion herein shall remain the property of Orion.**

© 2024 Orion Engineered Carbons GmbH



[www.orionsa.com](http://www.orionsa.com)